

Chapter 2

Hydrogenation of Renewables

Andreas J. Vorholt and Arno Behr

2.1 Introduction

Hydrogenation reactions have a variety of applications in the chemical industry which is shown by the corresponding products, such as ammonia, methanol, and polyamides. In petrochemistry, the addition of hydrogen is used to adjust properties of product mixtures, e.g. in the hydrocracking or hydrotreating. For renewables the same is already feasible or first proofs of concept were already shown. Therefore, hydrogenations indicate ways to increase the availability and enhance handling of products from natural resources. Heterogeneously catalysed hydrogenations with renewables are realised already in big scale, e.g. in the production of margarine or sorbitol.

In general, hydrogenation is the addition of hydrogen to C–C-, C–O-, C–N-, or N–O-multiple bonds. If the bond is broken, the reaction is referred to as hydrogenolysis [1]. Hydrogenation reactions are usually exothermic; therefore, low temperatures favour the reaction over its corresponding back reaction, which is dehydrogenation (Fig. 2.1).

Hydrogenations on industrial scale are mostly heterogeneously catalysed but lack of reactivity at mild reaction conditions or selectivity. Therefore, homogeneous catalysed hydrogenations are needed for more specialised reactions, which are required for the valorisation of renewables.

Common catalyst metals for homogeneous hydrogenations are platinum, palladium, rhodium, iridium, and ruthenium. But also non-precious metal systems as nickel, copper and other transition metals, such as molybdenum and cobalt have found applications in industrial processes. Frequently used homogeneous catalyst complexes in hydrogenation are as follows:




Fig. 2.1 General reaction equation of hydrogenation

- Wilkinson-type catalysts like $\text{RhCl}(\text{PPh}_3)_3$ and the corresponding ruthenium or iridium species
- Hydride species like $\text{Rh}(\text{CO})_2(\text{PPh}_3)\text{H}$
- Chelate complexes with chiral ligands like the Binaphos (see Fig. 2.4)
- Ru-Carbene complexes
- Special pincer ligands have high activity in the hydrogenation of, for example, CO_2 .

The present chapter is structured by the substrates of hydrogenation. In the first part, CO_2 as an inactive resource with carbon in a high oxidative state and with a low energy content as substrate is described. In this respect, homogeneous catalysts are able to gain valuable chemicals from this side product of burning or fermentation processes, e.g. methanol or formic acid.

The second part describes processing renewables, such as fatty acids and lignin via hydrogenation. These highly complex mixtures that contain various molecules and are oxygen rich compared to petrochemicals are defunctionalised or depolymerised via hydrogenation in order to gain more uniform blends.

2.2 Hydrogenations of Carbon Dioxide

Back in the 1980s, there were just a few research groups who dealt with the conversion of the “inactive” CO_2 [2–7]. The flashlight on carbon dioxide utilisation was set during the climate discussion and the impact of carbon dioxide to the greenhouse effect. Numerous efforts were put in the development of catalysts to process CO_2 as a chemical feedstock [8–11]. Beside this development, also photochemical and electrochemical reactions are in the statu nascendi with various materials from metal complexes, organic compounds, and transition metal electrodes [12–29]. The homogeneously catalysed reduction of carbon dioxide focuses on formic acid and methanol as products. These C_1 - molecules can act as hydrogen storage, as these molecules are liquid at ambient conditions. While formic acid contains 4.4 wt% of hydrogen, methanol contains 12.6 wt%. The stored hydrogen preferably originates from the electrolysis of water using solar energy from where a lot of effort is invested lately [27, 30–35]. The synthesis of formic acid [36] formate salts [37, 38] or methanol [39, 40] is entropically disfavoured, wherefore different bases are applied in the formation of formic acid (Fig. 2.2). If water is used as solvent, the carbonate/bicarbonate equilibrium also plays a role in the hydrogenations. Calculations showed that hydrogenation of the bicarbonate to formates is exergonic [41].


The formation of formic acid (FA) and formate amine salts was numerously studied in the last years. Also systems of hydrogenation and dehydrogenation with one catalyst system were developed. The following Table 2.1 gives an overview on several catalyst systems.



$$\Delta G^0 = 32.8 \text{ kJ mol}^{-1}$$

$$\Delta H^0 = -31.5 \text{ kJ mol}^{-1}$$


$$\Delta S^0 = -216 \text{ J mol}^{-1} \text{ K}^{-1}$$



$$\Delta G^0 = -9.5 \text{ kJ mol}^{-1}$$

$$\Delta H^0 = -84.3 \text{ kJ mol}^{-1}$$

$$\Delta S^0 = -250 \text{ J mol}^{-1} \text{ K}^{-1}$$



$$\Delta G^0 = -9.5 \text{ kJ mol}^{-1}$$

$$\Delta H^0 = -131 \text{ kJ mol}^{-1}$$

$$\Delta S^0 = -409 \text{ J mol}^{-1} \text{ K}^{-1}$$

Fig. 2.2 Gibbs energy of the hydrogenation of CO₂

First attempts to hydrogenate CO₂ were already made by Inoue in 1976 by applying triphenylphosphine with Ru-, Ir-, and Rh-complexes in benzene. The solvents applied in this hydrogenation of CO₂ play a crucial role for stabilising intermediate catalytic species. The Wilkinson complex has higher reaction rates in more polar solvents like methanol [43]. Also supercritical CO₂ itself as solvent in its state is possible, wherein also hydrogen is highly soluble [47]. The group of Jessop reported a TOF up to 95.000 h⁻¹ with RuCl₂(OAc)(PMe₃)₄ as catalyst precursor with different amines and alcohols [48]. The role of these additives is still object of investigation, but it is reported that the formate generation needs a Lewis base, while the alcohol additive is proton donor.

The role of water in the solvent mixtures was investigated since faster reactions were reported if water was present [56]. Reactions in water were first shown in the

Table 2.1 Catalyst systems for the formation of formic acid and its salts from CO₂ for abbreviations see Figs. 2.4 and 2.5

Catalyst precursor	Solvent	Additive	Phosphine ligand	P (H ₂ /CO) MPa	T/°C	Rct. time/h	TON	TOF/h ⁻¹	References
RuH ₂ (PPh ₃) ₄	C ₆ H ₆	Et ₃ N/H ₂ O		2.5/2.5	rt	20	87	4	[42]
RhCl(PPh ₃) ₃	DMSO	Et ₃ N		2/4	25	20	2.500	125	[43]
[Rh(cod)Cl] ₂ /dppb	DMSO	Et ₃ N		2/2	rt	22	1.150	30–47	[44]
RhCl(tppts) ₃	H ₂ O	NHMe ₂		2/2	rt	12	3.440	290	[45, 46]
I ₂ (PMe ₃) ₄	scCO ₂	Et ₃ N		8.5/12	50		7.200	1.040	[47]
RuCl(OAc) (PMe ₃) ₄	scCO ₂	Et ₃ N/C ₆ F ₅ OH		7/12	50	0.33	32.000	95.000	[48]
[RuCl ₂ (tppms) ₂] ₂	H ₂ O	NaHCO ₃		6/3.5	80	0.03		9.600	[49]
Fe(BF ₄) ₂ /PP ₃	MeOH	NaHCO ₃		6/0	80	20	610	30	[50]
IrH ₃ (P1)	H ₂ O/THF	KOH		4/4	120	48	3.500.000	73.000	[51, 52]
RuH(CI)(CO)(P3)	DMF	DBU		2/2	70	2	38.600		[53]
RuH(CI)(CO)(P3)	DMF	DBU		3/1	120			11.00000	[54]
			Nitrogen ligand						
[Cp*Ir(DHPT)Cl] ⁺	H ₂ O	KOH		3/3	120	48	222.000	(33.000)	[55]

early 1990 by Leitner with rhodium and sulfonated phosphine ligands (see Fig. 2.4), [57], and this concept was transferred to other ligands and metals [45, 49, 58–61]. TOFs of up to 9.600 h^{-1} were found with $[\text{RuCl}_2\text{TPPMS}_2]_2$. Besides, the sulfonated ligands also water-soluble amine-based ligands were used [62–65]. Beller and Laurenczy showed that if $[\text{RuCl}_2(\text{C}_6\text{H}_6)]_2$ is used also simple phosphine ligands such as TPP can form an active catalyst system in an aqueous NaHCO_3 solution. The ligand diphenylphosphinomethane DPPM showed TOFs of up to 1.260 h^{-1} but is fast deactivated. However, also phosphite ligands are reported [66].

The combination of ionic liquids (IL) and sulfonated ruthenium phosphine complexes was used to form a continuous operated process to gain pure formic acid under supercritical conditions (Fig. 2.3).

The optimisation of the process parameters was performed in a batch mode, especially the identification of the suitable IL. The 1-ethyl-3-methylimidazolium chloride (EMIMCl) was selected while the anion HCO_2^- showed the highest activity under continuous conditions. The extraction of the formic acid was the limiting factor of this system [67].

The group of Hicks established another concept of catalyst recycle by the immobilisation of Ir-complexes on mesoporous silica tethered surfaces. These concepts give a TON of 2800 after 20 h [68]. Laurenczy proved with the $[\text{RuCl}_2(\text{PTA})_4]$ (see Fig. 2.4) the stability of the complex by producing FA without base under mild conditions. This system was recycled four times showing a constant activity [69].

Another step to a commercial hydrogenation of carbon dioxide is the use of non-precious metals as catalyst metal due to their lower cost. These opportunities were investigated by Beller with Co-precursors and PP_3 (see Fig. 2.4) as ligand which yield a TON of over 3.500 [70]. If very strong bases like the Verkade base are applied with 2 MPa CO_2/H_2 , a TOF of 74.000 h^{-1} was achieved [71]. Also Fe complexes show activity in the hydrogenation with TONs of up to 7.500 [72].

Pincer ligands (see Fig. 2.5) are another highly promising aspect of hydrogenation of CO_2 since Nozaki reported on the trihydride iridium species with the PNP-pincer ligand (2,6-bis(diisopropylphosphinomethyl)pyridine) which showed the highest reported TOF (150.000 h^{-1}) and TON (3.5 mio after 48 h) at a temperature of $200\text{ }^\circ\text{C}$ and 8 MPa in THF/water [51, 52]. In the following, also, other air-stable pincer ligands with lower activities were reported [73] and pincer ligands

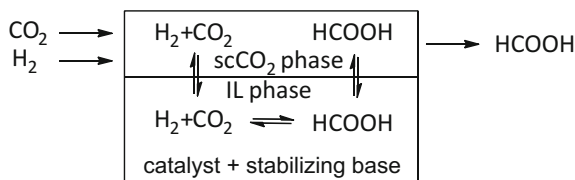


Fig. 2.3 Continuous-flow hydrogenation of CO_2 to formic acid based on a biphasic reaction system

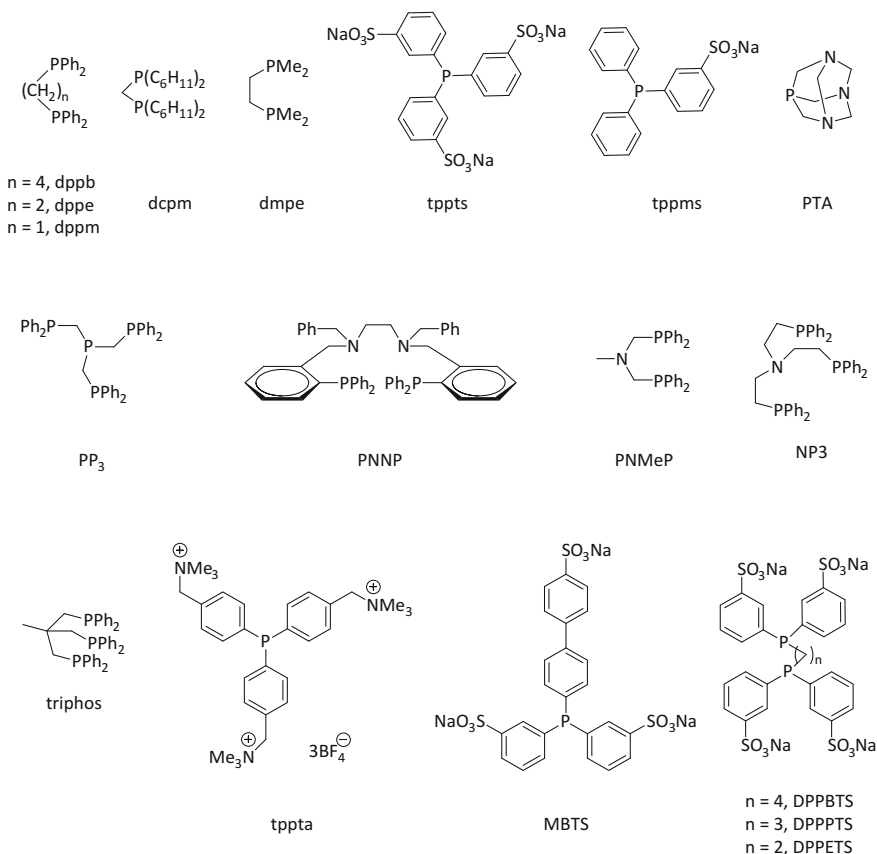


Fig. 2.4 Active phosphine ligands in the hydrogenation of CO_2

which use Fe as a catalyst metal [74]. Pidko reported on a Ru-based pincer catalyst which increases the TOF to $1.100.000 \text{ h}^{-1}$ in a DMF/DBU system [54].

Like in other field of homogeneous catalysis, N-heterocyclic carbenes were applied also in this field. The electron-donating ligands [75] showed with iridium TONs of up to 190.000 at 200°C and 6 MPa in 75 h [76, 77].

Only a few examples of N,N- or N,C-Ligands were reported so far [78–80]. These complexes are highly pH sensitive in respect of activity and solubility. The iridium-4DHBP catalyst complex $[\text{Cp}^*\text{Ir}(\text{4DHBP})\text{Cl}]\text{Cl}$ can be attributed to TOF of $42,000 \text{ h}^{-1}$ and TON of 190,000 at 120°C and 6 MPa. Noteworthy is activity of the catalyst at ambient temperature and pressure with the TOF of 7 h^{-1} . The pH switch can also be used as a trigger to precipitate such catalyst complexes in order to recycle them [81, 82]. While $[\text{Cp}^*\text{Ir}(\text{4DHBP})(\text{OH}_2)]^{2+}$ is still soluble in the water phase (1 ppm) even at optimised pH conditions, $[\text{Cp}^*\text{Ir}(\text{DHPT})(\text{Cl})]^+$ has a very low solubility in the product mixture of acidic FA/formate solution in a pH range of 4–7 (lowest concentration at pH 5 with 100 ppb). The filtration of the catalyst had

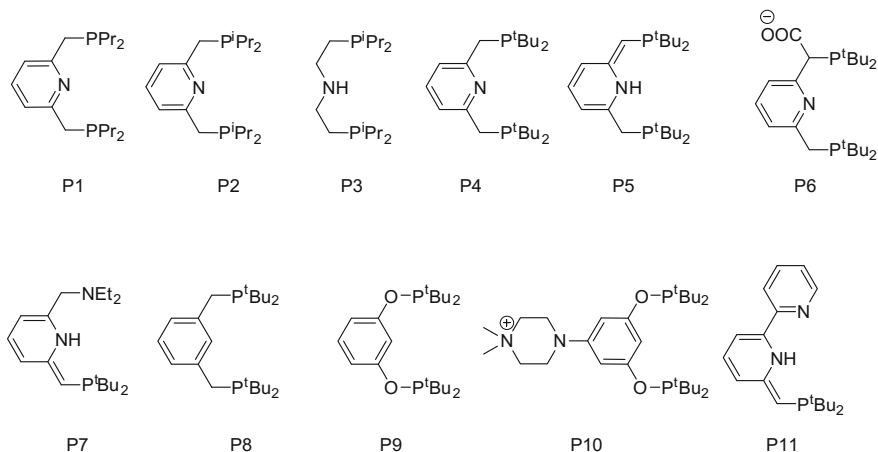


Fig. 2.5 Hydrogenation active pincer ligands

an efficiency of 91% after three runs, and the activity was retained over these recycling runs [55].

2.2.1 Interconversion of CO_2 /Formic Acid as Hydrogen Storage

In order to use the hydrogenation of CO_2 as liquid hydrogen storage not only the reaction to formic acid (FA) is important, but also the dehydrogenation of FA plays an important role [83, 84]. The concept of interconversion with one catalyst system was first realised by Leitner who used a Rh/DPPB catalyst system in a FA/ NEt_3 /acetone mixture in order to gain a hydrogenation TOF of 54 h^{-1} and a dehydrogenation TOF of 40 h^{-1} [85]. The very effective NPN Pincer iridium catalyst system for the hydrogenation is not active in the dehydrogenation [52]. If other additives like triethanolamine or NaOH are used, TOFs of up to 1.000 h^{-1} were observed for the dehydrogenation (Fig. 2.6).

The systems can be switched from hydrogenation to dehydrogenation by temperature and pressure [86, 87] or pH value [88]. Olah and co-workers presented a temperature controlled reversible hydrogen storage system in which a Ru pincer complex catalysed the hydrogenation of CO_2 in a water/THF system at $70\text{--}85^\circ\text{C}$ and 4–8 MPa. The dehydrogenation is executed at 69°C with the same catalyst complex. The recovery of the formed FA was completed after 4.5 h with 90% yield and could be repeated for six times with a total TON of 11.500.

The pH-controlled system is using the circumstance that at high pH values the hydrogenation is favoured while at low pH the dehydrogenation is faster (Fig. 2.7). This behaviour was shown with the $[(\text{Cp}^*\text{IrCl})_2(\text{THBPM})]^{2+}$ complex which is

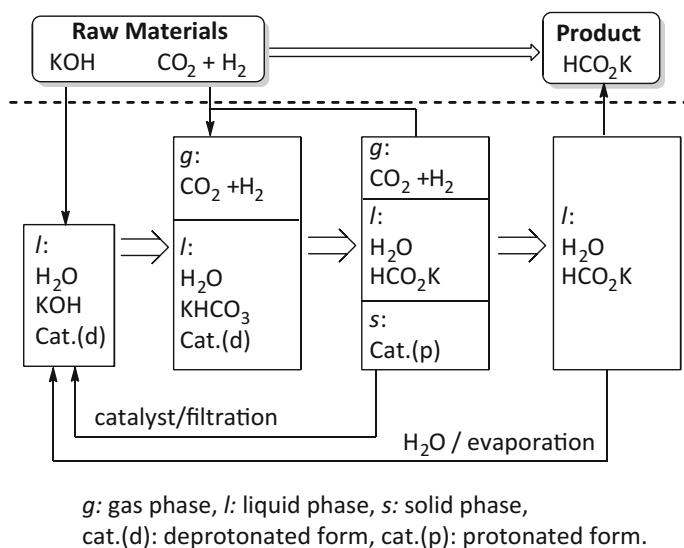


Fig. 2.6 Recycling system for the conversion of CO_2/H_2 into HCO_2K using $[\text{Cp}^*\text{Ir}(\text{DHPT})(\text{Cl})]^+$ in aqueous KOH solution


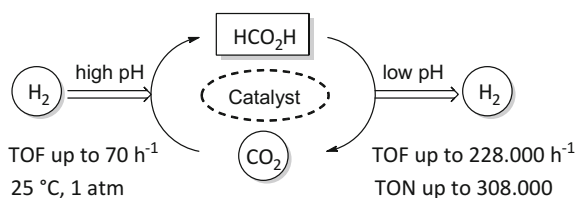


Fig. 2.7 pH-controlled hydrogen storage

active at ambient conditions with a TOF of 70 h^{-1} towards the FA and a TOF for the dehydrogenation of 228.000 h^{-1} at 90°C and low pH value. This cycle was repeated twice by adding acid or base to the system, respectively.

2.2.2 Methanol

The hydrogenation of formic acid, urea, or CO_2 can also be used to yield methanol in a more sustainable fashion in comparison with the route via syngas, which is gained from the partial oxidation of naphtha or steam reforming of methane. The



$$\Delta G_{298}^0 = -23.5 \text{ kcal mol}^{-1}$$

Fig. 2.8 Disproportionation of formic acid to methanol

examples to use homogeneous catalysis in this case are rare, but these examples are qualified by high efficiency.

For urea derivatives, organic carbonates, carbamates, and formates as products from carbon dioxide, Milstein showed that a PNN-Ru(II) pincer complexes $[\text{Ru}(\text{P7})(\text{H})-(\text{CO})]$ and $[\text{Ru}(\text{P11})(\text{H})(\text{CO})]$ produce methanol under mild conditions [89]. The high TON of 4,400 for the substrate dimethyl carbonate at 5 MPa, H_2 at 110 °C, is a promising example on the indirect hydrogenation [89].

The use of the above-described FA route in combination with the followed disproportionation of FA yields methanol [90] (Fig. 2.8). After the first investigation with iridium catalysts [90], Cantat reported a significantly improved precursor $[\text{Ru}(\text{cod})(\text{methylallyl})_2]$, with triphos ($\text{CH}_3\text{C}(\text{CH}_2\text{PPh}_2)_3$) as ligand and MSA (methanesulfonic acid) as catalytic system [91].

The direct hydrogenation of CO_2 without any intermediates is also part of the efforts of the academic community. At first, a tandem reaction was designed consisting of three steps: hydrogenation of CO_2 to FA (a); esterification to the formate ester (b); hydrogenation of the formate ester to methanol (c) [92]. The total TON for the whole cascade reaction was 2.5 in respect of methanol in a one-pot reaction (Fig. 2.9).

The direct hydrogenation of CO_2 was initially shown by the Leitner group while the hydrogenation to methanol is conducted within one catalytic cycle (Fig. 2.10).

The ligand triphos is the game-changer in this synthesis and in cooperation with the additives gives a TON for the ruthenium complex of 603. The activity of this catalyst system is comparable to the heterogeneous catalyst systems.

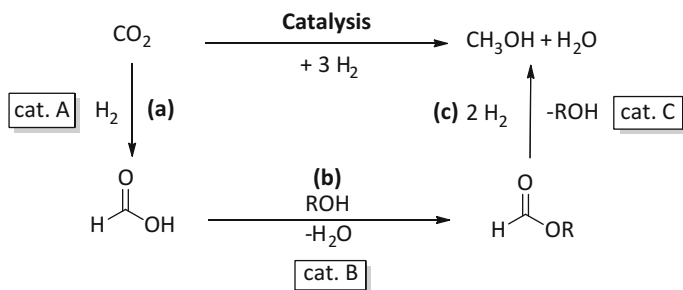


Fig. 2.9 Three-step tandem catalysis

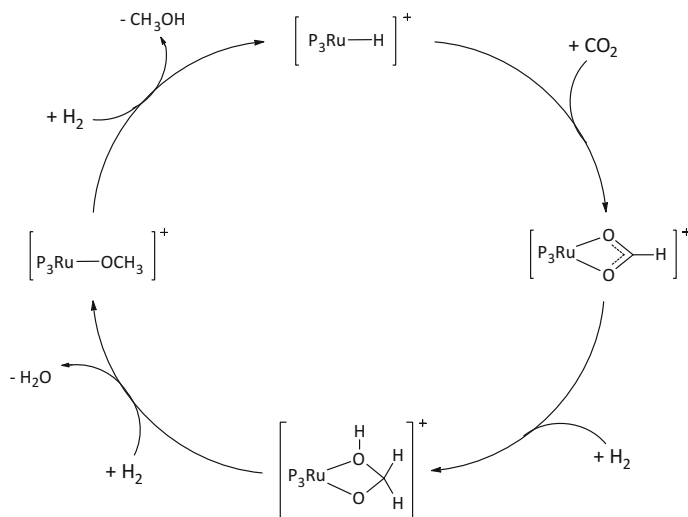


Fig. 2.10 MeOH production from direct catalytic hydrogenation of CO₂ and proposed mechanism

2.3 Lignin

As lignin is a complex three-dimensional amorphous polymer that consists of methoxylated phenylpropanoids (see Chap. 1.3.4), it is a hard task to generate valuable chemical products or products blends [93]. Since lignin is the only widespread renewable with aromatic moieties, several approaches were made to depolymerise lignin as alternative to the petrochemically produced aromatics [94, 95]. Hydrotreating is one possibility to produce chemicals with low molecular weight from lignin. These processes are also named hydrodeoxygenation, hydrogenation, and hydrogenolysis depending on the molecular structure to be cleaved. The monomers from lignin are usually linked by ether or by C–C bonds. The majority of almost two-thirds or more are ether bonds. The review of Zhang beautifully shows differences of the linkages (Fig. 2.11) [96].

The big challenge in the valorisation of lignin is the different linkages of the polymeric structure and the big variety of the compositions of lignin depending on plant type, part of the plant, etc. [97, 98].

The homogeneous-based systems for hydrogenation of lignin compounds are relatively rare in comparison with the heterogeneous catalyst systems [99]. Table 2.2 shows recent examples of homogeneous catalysts with model substrates. Only few catalyst systems are ready to work with processed lignin from, e.g., the Kraft process.

Hu hydrogenated lignin model compounds such as 4-propylphenol, eugenol, 1,2-dimethoxy-4-propylbenzene, and 2,6-dimethoxy-4-propylphenol at 298 K with a di- μ -chlorobis(η^4 -1,5-hexadiene)-dirhodium(I) complex. In a solvent system of hexane/water, mostly double bond and the aromatic rings were hydrogenated. This

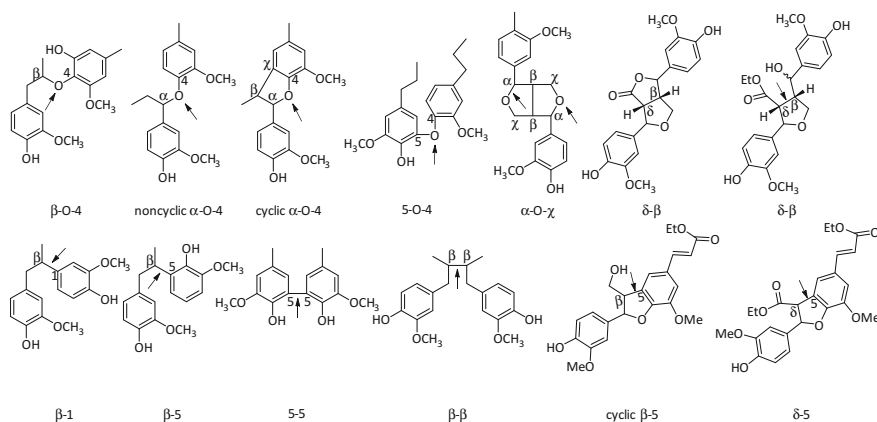


Fig. 2.11 Typical linkages between the primary units of lignin

reactivity is not beneficial due to the point that no cleavage has occurred and hydrogen has been consumed. Further examples used other model substrates, such as phenol, anisole, and anthracene [102–105, 108, 109].

The group of Nagy used besides Raney Ni, Pt/C, and NaBH₄/I₂ also the homogeneous hydrogenation catalyst Ru(PPh₃)₃Cl₂ in the hydrogenation of organosolv lignin in order to significantly reduce the molecular weight of the lignin. This catalyst was able to cleave 4-O-5- and aryl-O-aliphatic linkages to decrease oxygen content in the product mixture [106].

Nickel complexes with a N-heterocyclic carbene (SIPr·HCl) and NaOtBu as an additive are also active in the hydrogenolysis of diaryl ethers [107]. At 0.1 MPa, H₂ yields of 54–99% for the corresponding phenols and arenes were reported by Hartwig. The cleavage activity for aromatic C–O bonds of this system is in the order of Ar–OAr ≫ Ar–OMe > ArCH₂–OMe. Comparable heterogeneous Ni catalyst showed different selectivities to the diol instead of the phenol (Fig. 2.12) [110].




The group of Marks developed a nice way to process aliphatic ethers or furans with a tandem strategy of homogenous and heterogeneous catalysis. The homogeneous catalyst is a transition metal triflate that decyclises the C–O bond in the furan while the supported Pd nanoparticle catalyst hydrogenates the resulting double bond. This reaction is conducted in a stabilising IL and yields linear alcohols with no loss of any aromaticity (Fig. 2.13) [111, 112].

These reactivities are dedicated to cleave β-O-4 ethanol aryl ethers and do not affect the aromatic rings in the substrates [113, 114]. Popular catalyst systems are Ru(Cl)₂(PPh₃)₃, RuH₂(CO)(PPh₃)₃, and Ru-Xantphos, as shown in Fig. 2.14.

A new reactivity was lately shown by Leitner by addressing the C–C Bond in β-O-4-linked molecules. The Ru triphos complex showed again, as already shown in the CO₂ hydrogenation, a unique reactivity (Fig. 2.15) [115].

Different substrates were applied with high selectivities for the cleavage of the C–C bonds. These developments show the possibility to address several linkages in lignin by homogeneous catalysis.

Table 2.2 Homogeneous catalytic systems for the hydrogenation of lignin and their corresponding model substrates

Catalyst	Reaction conditions			Substrate	Products	Conv. (%)	Notes	References
	<i>T</i> (K)	<i>P</i> (MPa)	<i>t</i> (min)/solvent					
(1,5-hexadiene) RhCl dimer ^a	<i>f</i>	0.1	<i>g</i>	Phenol	cyclohexanol	<i>g</i>		[100]
Colloidal rhodium	<i>f</i>	5	<i>g</i>	Methylanisole	Methylcyclohexane, 1-methyl-2-methoxycyclohexane ^b	100		[101]
[(1,5-C ₆ H ₁₀) RhCl] ₂ ^b	<i>f</i>	0.1	3000	2-methoxy-4-propylphenol	Methylcyclohexane, 1-methyl-2-methoxycyclohexane ^b	100		[102]
Oxo-trirrhodium (III)acetate ^c	313	0.1	<i>g</i>	Anthracene	<i>cis</i> -2-methoxy- <i>cis</i> -4-propylcyclohexanol, <i>cis</i> -2-methoxy- <i>trans</i> -4-propylcyclohexanol	<i>g</i>	<i>i</i>	[103]
[(C ₆ H ₆) ₄ Ru ₄ H ₄] Cl ₂ ^d	363	6	14	Acetophenone	1,2,3,4-tetrahydroanthracene, 1,2,3,4,5,6,7,8-octahydroanthracene	64		[104]
[(C ₆ H ₆) ₄ Ru ₄ H ₄] Cl ₂ ^d	363	6	14	Anisole	Methylcyclohexylketone, Phenylethanol, Cyclohexylethanol	22		[104]
Rhodium nanoparticles ^e	348	4	600	4-methoxyphenol	Methoxycyclohexane	21		[105]
RuCl ₂ (PPh ₃) ₃	<i>f</i>	5	<i>g</i>	Ethanol organosolv lignin	4-methoxy-cyclohexanol, 1-methoxy-4-cyclohexenol	<i>g</i>	<i>j</i>	[106]
Ni(COD) ₂ , SIP• HCl	120	0.1	<i>m</i> -Xylene		Lower Mw lignin	>85	R=H, Me, <i>m</i> -OMe, CF ₃	[107]
Ni(COD) ₂ , SIP• HCl	120	0.1	<i>m</i> -Xylene			100	Alk=Hexyl, Me	[107]

(continued)

Table 2.2 (continued)

Catalyst	Reaction conditions			Substrate	Products	Conv. (%)	Notes	References
	T (K)	P (MPa)	t (min)/solvent					
Ni(COD) ₂ , SIP ^{••} HCl	120	0.1	<i>m</i> -Xylene			85	Alk=Hexyl	[107]
Ni(COD) ₂ , SIP ^{••} HCl	120	0.1	<i>m</i> -Xylene			>85	R ¹ =Bu, H; R ² =Ph, Me; R ³ =H, Et	[107]

^aWith phase transfer catalyst. ^bWith Bu₄NHSO₄ phase transfer agent. ^cActive after reduction with H₂. ^dBiphasic conditions. ^eIn ionic liquids. ^fRoom temperature. ^gNot specified. ^hTwo isomers. ⁱExtremely air sensitive. ^jMore hydroxyl groups. SIP^{••}HCl = 1,3-Bis(2,6-diisopropylphenyl)imidazolidinium chloride

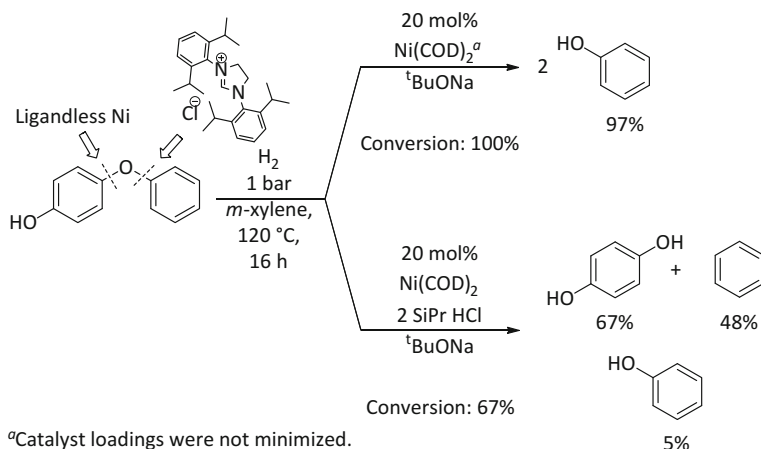


Fig. 2.12 Selectivities in nickel-catalysed hydrogenation

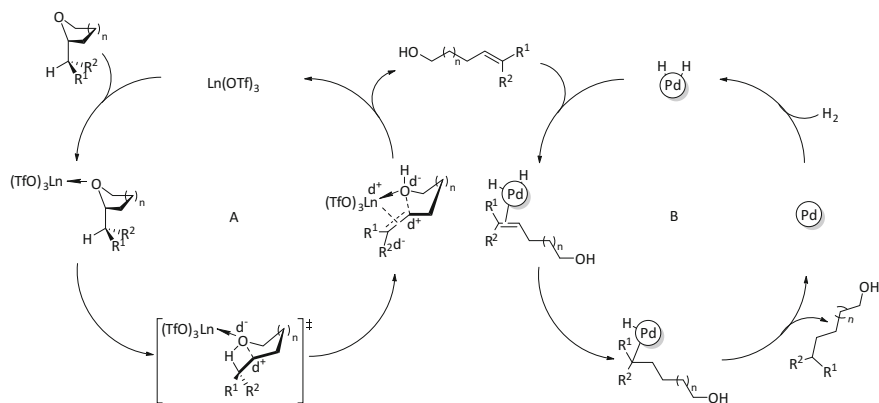


Fig. 2.13 Proposed tandem pathway for lanthanide triflate/Pd nanoparticle-mediated etheric C–O bond hydrogenolysis

2.4 Sugars

The conversion of cellulose, starch, or the corresponding oligo- and mono-sugars by hydrogenation with homogeneous catalysts is rarely reported. Hydrogenation of carbohydrates can be divided into the conversion of polymers into degraded products or monomers and further processed derivatives like HMF. The depolymerisation of cellulose is acid catalysed hydrogenolysis to fermentable sugars [116]. For the conversion of mono-sugars such as glucose in big scale processes to yield, e.g. the sweetener sorbitol, heterogeneous catalyst are used.

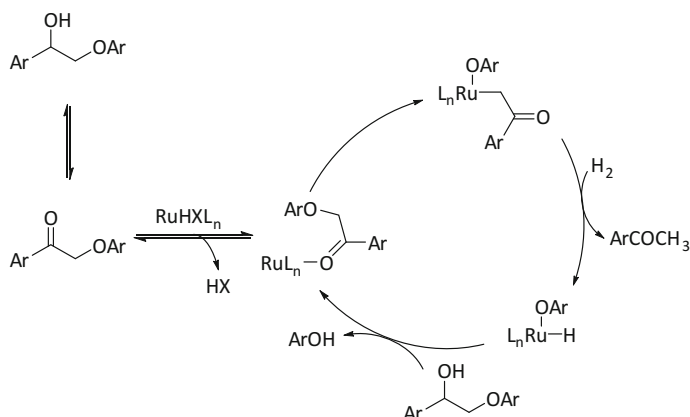


Fig. 2.14 Mechanism of Ru-catalysed C-O-bond cleavage of lignin-related polymers

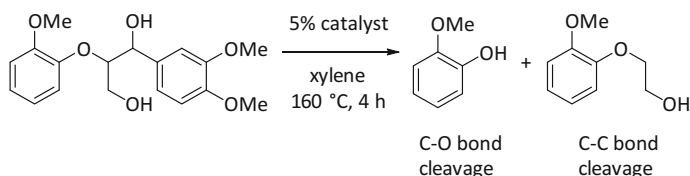


Fig. 2.15 Hydrogenation of lignin surrogate by Ru triphos

An example using homogeneous catalysis for depolymerisation was shown by Jiang to yield alcohols by applying 80–120 bar hydrogen with nickel salts. The intermediates glucose and xylose were hydrogenated in one pot to sorbitol and xylitol in yields up to 87.9% [117] (Fig. 2.16).

Furthermore, homogeneous reactions with platform intermediates from sugar are reported, as like HMF [118] to caprolactam. Also fragrances and pharmaceuticals can be synthesised incorporating homogenous catalysis [119].

2.5 Fats

The hydrogenation of unsaturated fats and oils is a well-established process in oleo chemistry and is called “hardening”. This process is used in the nutrition industry for producing margarine. Liquid unsaturated oils are converted into their corresponding saturated fats. The common catalyst for this process is Raney nickel, while some processes also use palladium particles [1]. A more challenging transformation is the selective conversion of polyunsaturated fatty acids into mono-unsaturated compounds (Fig. 2.17).

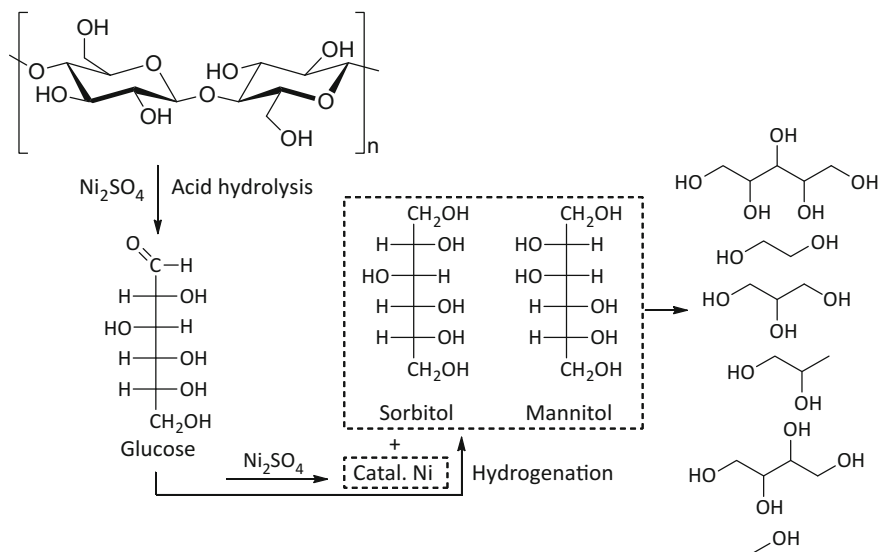


Fig. 2.16 Hydrogenation of cellulose to corresponding degradation products

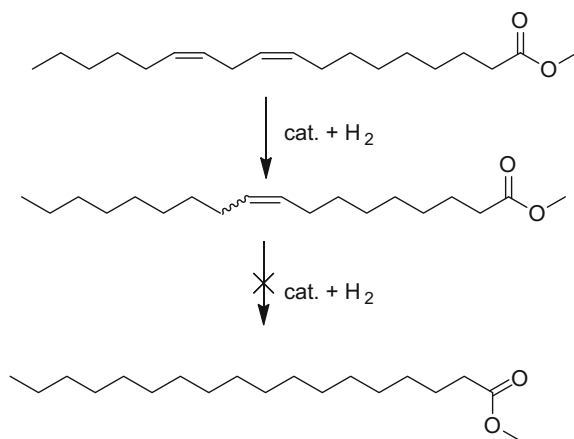


Fig. 2.17 Selective hydrogenation of methyl linoleate to C18:1—acid methyl ester

These reactions are catalysed by palladium carbonyls, platinum-tin systems, iron, and cobalt or nickel salts, which are activated by triethylaluminium [120–123]. Good results are observed with precious metal phosphine catalyst, for example, Wilkinson's catalyst [124]. High conversions of linoleic esters can be easily obtained with a palladium nanocatalyst. The catalytically active nanoparticles (diameter: 4 nm) are obtained by reducing palladium dichloride with hydrogen in DMF or propylene carbonate and an aqueous buffer. Sunflower oil with a linoleic

acid content of 70% is converted into 92% oleic acid with no detectable content of linoleic acid. These palladium nanoparticles are also suitable for recycling using a liquid/liquid technique [125–127].

2.6 Conclusions

In conclusion, the hydrogenation of renewables with homogeneous catalyst addresses several points for future greener chemistry. The upgrade of raw renewable polymers such as lignin or sugars is of high importance to use more of these good available feedstocks. Furthermore also defined high value molecules can be yielded by hydrogenation of the renewables. Specially, the hydrogenation of CO₂ will gain more importance in the future as possible energy storage or as starting point for C₁-building blocks.

References

1. Sanfilippo D, Rylander PN (2000) Hydrogenation dehydrogenation. In: Ullmann's encyclopedia of industrial chemistry. Wiley-VCH Verlag
2. Aresta M, Forti G (1987) Carbon dioxide as a source of carbon—biochemical and chemical uses. D. Reidel Publ, Dordrecht
3. Inoue S, Yamazaki Y (1982) Organic and bioorganic chemistry of carbon dioxide. Kodansha, Tokyo
4. Behr A (1987) Chem Eng Technol 10:16–27
5. Behr A (1988) Angew Chem 100:681–698
6. Behr A (1988) Carbon dioxide activation by metal complexes. VCH-Verlag, Weinheim, New York
7. Klankermayer J, Wesselbaum S, Beydoun K, Leitner W (2016) Angew Chem 55:7296–7343
8. Appel AM, Bercaw JE, Bocarsly AB, Dobbek H, DuBois DL, Dupuis M, Ferry JG, Fujita E, Hille R, Kenis PJA et al (2013) Chem Rev 113:6621–6658
9. Tsuji Y, Fujihara T (2012) Chem Commun 48:9956–9964
10. Behr A, Neuberg S (2009) Erdöl Erdgas Kohle 125:367–374
11. Aresta M (2010) Carbon dioxide as a chemical feedstock. Wiley-VCH, Weinheim
12. Benson EE, Kubiak CP, Sathrum AJ, Smieja JM (2009) Chem Soc Rev 38:89–99
13. Hori Y (2008) Mod Asp Electrochem 89–189
14. Morris AJ, Meyer GJ, Fujita E (2009) Acc Chem Res 42:1983–1994
15. Rakowski Dubois M, Dubois DL (2009) Acc Chem Res 42:1974–1982
16. Doherty MD, Grills DC, Muckerman JT, Polyansky DE, Fujita E (2010) Coord Chem Rev 254:2472–2482
17. Takeda H, Ishitani O (2010) Coord Chem Rev 254:346–354
18. Takeda H, Koike K, Morimoto T, Inumaru H, Ishitani O (2011) Inorg Photochem (eds.: van Eldik R, Stochel G), Academic Press, pp 137–186
19. Schneider J, Jia H, Muckerman JT, Fujita E (2012) Chem Soc Rev 41:2036
20. Tamaki Y, Morimoto T, Koike K, Ishitani O (2012) Proc Natl Acad Sci 109:15673–15678
21. Izumi Y (2013) Coord Chem Rev 257:171–186
22. Navalón S, Dhakshinamoorthy A, Álvaro M, García H (2013) ChemSusChem 6:562–577
23. Costentin C, Robert M, Savéant J-M (2013) Chem Soc Rev 42:2423–2436

24. Clark ML, Grice KA, Moore CE, Rheingold AL, Kubiak CP (1894) *Chem Sci* 2014:5
25. Protti S, Albini A, Serpone N (2014) *Phys Chem Chem Phys* 16:19790–19827
26. Das S, Wan Daud WMA (2014) *Renew Sustain Energy Rev* 39:765–805
27. Oh Y, Hu X (2013) *Chem Soc Rev* 42:2253–2261
28. Lu X, Leung DYC, Wang H, Leung MKH, Xuan J (2014) *ChemElectroChem* 1:836–849
29. Manbeck GF, Fujita EA (2015) *J Porphyrins Phthalocyanines* 19:45–64
30. Fujita E, Furenlid LR, Renner MW (1997) *J Am Chem Soc* 119:4549–4550
31. DiMeglio JL, Rosenthal J (2013) *J Am Chem Soc* 135:8798–8801
32. Costentin C, Passard G, Robert M, Savéant JM (2014) *J Am Chem Soc* 136:11821–11829
33. Rosen BA, Salehi-Khojin A, Thorson MR, Zhu W, Whipple DT, Kenis PJA, Masel RI (2011) *Science* 334:643–645
34. Grills DC, Matsubara Y, Kuwahara Y, Golisz SR, Kurtz DA, Mello BA (2014) *J Phys Chem Lett* 5:2033–2038
35. Costentin C, Drouet S, Robert M, Saveant JMA (2012) *Science* 338:90–94
36. Jessop PG, Iktariya T, Noyori R (1995) *Chem Rev* 95:259–272
37. Himeda Y (2007) *Eur J Inorg Chem* 3927–3941
38. Jessop PG, Joó F, Tai CC (2004) *Coord Chem Rev* 248:2425–2442
39. Li Y-N, Ma R, He L-N, Diao Z-F (2014) *Catal Sci Technol* 4:1498
40. Choudhury J (2012) *ChemCatChem* 4:609–611
41. Kovács G, Schubert G, Joó F, Pápai I (2006) *Catal Today* 115:53–60
42. Inoue Y, Izumida H, Sasaki Y, Hashimoto H (1976) *Chem Lett* 5:863–864
43. Ezhova NN, Kolesnichenko NV, Bulygin AV, Slivinskii EV, Han S (2002) *Russ Chem Bull Int Ed* 51:2165–2169
44. Graf E, Leitner W (1992) *J Chem Soc Chem Commun* 623–624
45. Leitner W, Dinjus E, Gassner F (1998) *Aqueous-Phase Organomet Catal Concepts Appl Wiley-VCH, Weinheim*, pp 486–498
46. Jessop PG (2007) *Handbook homogeneous hydrogenation* (De Vries JG, Elsevier CJ, eds). Wiley-VCH, Weinheim, pp 489–511
47. Jessop PG, Ikariya T, Noyori R (1994) *Nature* 368:231–233
48. Munshi P, Main AD, Linehan JC, Tai CC, Jessop PG (2002) *J Am Chem Soc* 124:7963–7971
49. Elek JJ, Nádasdi L, Papp G, Laurenczy G, Joó F (2003) *Appl Catal A* 255:59–67
50. Federsel C, Boddien A, Jackstell R, Jennerjahn R, Dyson PJ, Scopelliti R, Laurenczy G, Beller M (2010) *Angew Chem Int Ed* 49:9777–9780
51. Tanaka R, Yamashita M, Nozaki K (2009) *J Am Chem Soc* 131:14168–14169
52. Tanaka R, Yamashita M, Chung LW, Morokuma K, Nozaki K (2011) *Organometallics* 30:6742–6750
53. Filonenko GA, Hensen EJM, Pidko EA (2014) *Catal Sci Technol* 4:3474–3485
54. Filonenko GA, van Putten R, Schulpfen EN, Hensen EJ, Pidko EAM (2014) *ChemCatChem* 6:1526–1530
55. Himeda Y, Onozawa-Komatsuzaki N, Sugihara H, Kasuga K (2007) *Organometallics* 26:702–712
56. Tsai JC, Nicholas KM (1992) *J Am Chem Soc* 114:5117–5124
57. Gassner F, Leitner W (1993) *J Chem Soc Chem Commun* 1465–1466
58. Józai I, Joó F (2004) *J Mol Catal A Chem* 224:87–91
59. Kathó Á, Opre Z, Laurenczy G, Joó F (2003) *J Mol Catal A Chem* 204–205:143–148
60. Joó F, Laurenczy G, Karády P, Elek J, Nádasdi L, Roulet R (2000) *Appl Organomet Chem* 14:857–859
61. Joó F, Laurenczy G, Nadasdi L, Elek J (1999) *Chem Commun* 971–972
62. Laurenczy G, Joo F, Nadasdi L (2000) *Inorg Chem* 39:5083–5088
63. Horváth H, Laurenczy G, Kathó Á (2004) *J Organomet Chem* 689:1036–1045
64. Erlandsson M, Landaeta VR, Gonsalvi L, Peruzzini M, Phillips AD, Dyson PJ, Laurenczy G (2008) *Eur J Inorg Chem* 2008:620–627
65. Laurenczy G, Jedner S, Alessio E, Dyson PJ (2007) *Inorg Chem Commun* 10:558–562

66. Muller K, Sun Y, Thiel WR (2013) *ChemCatChem* 5:1340–1343
67. Wesselbaum S, Hintermair U, Leitner W (2012) *Angew Chem Int Ed* 51:8585–8588
68. Xu Z, McNamara ND, Neumann GT, Schneider WF, Hicks JC (2013) *ChemCatChem* 5:1769–1771
69. Moret S, Dyson PJ, Laurénczy G (2014) *Nat Commun* 5:4017
70. Federsel C, Ziebart C, Jackstell R, Baumann W, Beller M (2012) *Chem A Eur J* 18:72–75
71. Kisanga PB, Verkade JG, Schwesinger R (2000) *J Org Chem* 65:5431–5432
72. Ziebart C, Federsel C, Anbarasan P, Jackstell R, Baumann W, Spannenberg A, Beller M (2012) *J Am Chem Soc* 134:20701–20704
73. Schmeier TJ, Dobereiner GE, Crabtree RH, Hazari N (2011) *J Am Chem Soc* 133: 9274–9277
74. Langer R, Diskin-Posner Y, Leitus G, Shimon LJW, Ben-David Y, Milstein D (2011) *Angew Chem Int Ed* 50:9948–9952
75. Sanz S, Azua A, Peris E (2010) *Dalton Trans* 39:6339–6343
76. Azua A, Sanz S, Peris E (2011) *Chem A Eur J* 17:3963–3967
77. Sanz S, Benítez M, Peris E (2010) *Organometallics* 29:275–277
78. Bolinger CM, Sullivan BP, Conrad D, Gilbert JA, Story N, Meyer TJ (1985) *J Chem Soc Chem Commun* 796–797
79. Hayashi H, Ogo S, Abura T, Fukuzumi S (2003) *J Am Chem Soc* 125:14266–14267
80. Wang WH, Ertem MZ, Xu S, Onishi N, Manaka Y, Suna Y, Kambayashi H, Muckerman JT, Fujita E, Himeda Y (2015) *ACS Catal* 5:5496–5504
81. Zuwei X, Ning Z, Yu S, Kunlan L (2001) *Science* 292:1139–1141
82. Wang W, Zhang G, Lang R, Xia C, Li F (2013) *Green Chem* 15:635
83. Williams R, Crandall RS, Bloom A (1978) *Appl Phys Lett* 33:381–383
84. Bi QY, Lin JD, Liu YM, Du XL, Wang JQ, He HY, Cao Y (2014) *Angew Chem Int Ed* 53:13583–13587
85. Leitner W, Dinjus E, Gassner F (1994) *J Organomet Chem* 475:257–266
86. Hsu SF, Rommel S, Eversfield P, Muller K, Klemm E, Thiel WR, Plietker B (2014) *Angew Chem Int Ed* 53:7074–7078
87. Enthaler S, Brück A, Kammer A, Junge H, Irran E, Güllak S (2015) *ChemCatChem* 7:65–69
88. Maenaka Y, Suenobu T, Fukuzumi S (2012) *Energy Environ Sci* 5:7360
89. Balaraman E, Gunanathan C, Zhang J, Shimon LJW, Milstein D (2011) *Nat Chem* 3:609–614
90. Miller AJM, Heinekey DM, Mayer JM, Goldberg KI (2013) *Angew Chem Int Ed* 52: 3981–3984
91. Savourey S, Lefèvre G, Berthet JC, Thuéry P, Genre C, Cantat T (2014) *Angew Chem Int Ed* 53:10466–10470
92. Huff CA, Sanford MS (2011) *J Am Chem Soc* 133:18122–18125
93. Achyuthan KE, Achyuthan AM, Adams PD, Dirk SM, Harper JC, Simmons BA, Singh AK (2010) *Molecules* 15:8641–8688
94. Holladay JE, White JF, Bozell JJ, Johnson D (2007) Top value-added chemicals from biomass—volume II results of screening for potential candidates from biorefinery lignin, Richland, WA
95. Gasser CA, Hommes G, Schäffer A, Corvini PFX (2012) *Appl Microbiol Biotechnol* 95:1115–1134
96. Li C, Zhao X, Wang A, Huber GW, Zhang T (2015) *Chem Rev* 115:11559–11624
97. Stewart D (2008) *Ind Crops Prod* 27:202–207
98. Calvo-Flores FG, Dobado JA (2010) *ChemSusChem* 3:1227–1235
99. Zakzeski J, Bruijninx PCA, Jongerius AL, Weckhuysen BM (2010) *Chem Rev* 110: 3552–3599
100. Januszkievicz KR, Alper H (1983) *Organometallics* 2:1055–1057
101. Nasar K, Fache F, Lemaire M, Béziat J-C, Besson M, Gallezot P (1994) *J Mol Catal* 87: 107–115
102. Hu TQ, James BR, Rettig SJ, Lee C-L (1997) *Can J Chem* 75:1234–1239

103. Lamping AE, Guo X, Rempel GL (1994) *J Mol Catal* 87:75–93
104. Plasseraud L, Süß-Fink G (1997) *J Organomet Chem* 539:163–170
105. Zhao C, Wang HZ, Yan N, Xiao CX, Mu XD, Dyson PJ, Kou Y (2007) *J Catal* 250:33–40
106. Nagy M, David K, Britovsek GJP, Ragauskas AJ (2009) *Holzforschung* 63:513–520
107. Sergeev AG, Hartwig JF (2011) *Science* 332:439–443
108. Schulz J, Roucoux A, Patin H (2000) *Chemistry* 6:618–624
109. Suárez T, Guzmán A, Fontal B, Reyes M, Bellandi F, Contreras RR, Cancines P, León G, Rojas L (2006) *Transit Met Chem* 31:176–180
110. Sergeev AG, Webb JD, Hartwig JF (2012) *J Am Chem Soc* 134:20226–20229
111. Atesin AC, Ray NA, Stair PC, Marks TJ (2012) *J Am Chem Soc* 134:14682–14685
112. Li Z, Assary RS, Atesin AC, Curtiss LA, Marks TJ (2014) *J Am Chem Soc* 136:104–107
113. Nichols JM, Bishop LM, Bergman RG, Ellman JA (2010) *J Am Chem Soc* 132:12554–12555
114. Wu A, Patrick BO, Chung E, James BR (2012) *Dalton Trans* 41:11093
115. vom Stein T, den Hartog T, Buendia J, Stoychev S, Mottweiler J, Bolm C, Klankermayer J, Leitner W (2015) *Angew Chem Int Ed* 54:5859–5863
116. Huang Y-B, Fu Y (1095) *Green Chem* 2013:15
117. Jiang C (2014) *Cellul Chem Technol* 48:75–78
118. van Putten RJ, van der Waal JC, De Jong E, Rasrendra CB, Heeres HJ, De Vries JG (2013) *Chem Rev* 113:1499–1597
119. Shao X, Li Z, Qian X, Xu X (2009) *J Agric Food Chem* 57:951–957
120. Ahmad MM, Priestley TM, Winterbottom JM (1979) *J Am Oil Chem Soc* 56:571–577
121. Fedeli E, Jacini G (1976) *Fette, Seifen, Anstrichm* 78:30–34
122. Koritala S (1985) *J Am Oil Chem Soc* 62:517–520
123. Filip V, Zajic J (1987) *Fat Sci Technol* 89:220–224
124. Bland WJ, Dine TC, Jobanputra RN, Shone GG (1984) *J Am Oil Chem Soc* 61:924–928
125. Behr A, Döring N, Kozik C, Schmidtke H, Durowicz S (1991) Preparation of unsaturated fatty acids or derivatives by catalytic hydrogenation of polyunsaturated fatty acids or derivatives, DE4012873A1
126. Behr A, Lux A (2014) *Chem Ing Tech* 86:1933–1940
127. Behr A, Döring N, Durowicz-Heil S, Ellenberg B, Kozik C, Lohr C, Schmidke H (1993) *Fat Sci Technol* 95:2–12

<http://www.springer.com/978-3-319-54159-4>

Homogeneous Catalysis with Renewables

Behr, A.; Vorholt, A.J.

2017, VIII, 215 p. 205 illus., 16 illus. in color., Hardcover

ISBN: 978-3-319-54159-4